

ACCEPTED PAPER · SUPPLEMENTARY FILE

## Hydroxyapatite-alginate-gelatin bioinks for bioprinting: Printability, microarchitecture, dental pulp stem cells viability and morphology

*Paper version: Accepted Paper*

Accepted Papers are manuscripts accepted for publication, encompassing all changes made following the peer review process, along with a standard cover page indicating the paper version and an “Accepted Paper” watermark, but excluding any other editing, typesetting or other changes made by AccScience Publishing and/or authors post-acceptance.

**Article ID:** IJB026160140

**Citation:** Lugo A, Beltran JF, Jimenez L, *et al.* Hydroxyapatite-alginate-gelatin bioinks for bioprinting: Printability, microarchitecture, dental pulp stem cells viability and morphology. *Int J Bioprint.* 2026. doi: 10.36922/IJB026160140

**Copyright:** © 2026 Author(s). This is an Open Access article distributed under the terms of the Creative Commons Attribution License, permitting distribution, and reproduction in any medium, provided the original work is properly cited.

**Publisher’s Note:** AccScience Publishing remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

**Hydroxyapatite-alginate-gelatin bioinks for bioprinting: Printability, microarchitecture, dental pulp stem cells viability and morphology**

*Running title:* HAp composite bioinks: hDPSC bioprinting

**Supplementary File**

**Table S1.** Full experimental design matrix, replicate structure for cell-free scaffold morphometric characterization and printing outcomes

Cell-free bioink composition (%)	Nozzle	Extrusion speed (mm/s)	# of layers	# open pores	Pore size (µm)	Printability index	Pore area (mm <sup>2</sup> )	Pore perimeter (mm)
Alg-Gel-HAp(1)	20G	1	2	15	899	1.004	0.470	2.746
Alg-Gel-HAp(1)	20G	1	2	15	950	0.927	0.530	2.805
Alg-Gel-HAp(1)	20G	1	2	16	956	0.973	0.563	2.960
Alg-Gel-HAp(1)	20G	1	4	13	845	0.954	0.406	2.489
Alg-Gel-HAp(1)	20G	1	4	14	802	0.932	0.387	2.403
Alg-Gel-HAp(1)	20G	1	4	12	843	0.925	0.432	2.527
Alg-Gel-HAp(1)	20G	2	2	16	976	0.943	0.581	2.960
Alg-Gel-HAp(1)	20G	2	2	16	969	0.964	0.531	2.861
Alg-Gel-HAp(1)	20G	2	2	16	1044	0.948	0.618	3.062
Alg-Gel-HAp(1)	20G	2	4	12	875	0.973	0.458	2.672
Alg-Gel-HAp(1)	20G	2	4	10	928	0.966	0.523	2.841
Alg-Gel-HAp(1)	20G	2	4	11	909	0.908	0.509	2.719
Alg-Gel-HAp(1)	20G	3	2	16	1120	1.008	0.660	3.262
Alg-Gel-HAp(1)	20G	3	2	16	1052	0.965	0.674	3.227
Alg-Gel-HAp(1)	20G	3	2	16	999	0.964	0.578	2.985
Alg-Gel-HAp(1)	20G	3	4	11	924	0.981	0.517	2.850
Alg-Gel-HAp(1)	20G	3	4	12	909	0.964	0.451	2.637
Alg-Gel-HAp(1)	20G	3	4	12	903	0.923	0.491	2.691
Alg-Gel-HAp(1)	22G	1	2	16	1132	0.907	0.783	3.372
Alg-Gel-HAp(1)	22G	1	2	16	1112	0.891	0.778	3.330
Alg-Gel-HAp(1)	22G	1	2	16	1192	0.896	0.895	3.582
Alg-Gel-HAp(1)	22G	1	4	N.A.	N.A.	N.A.	N.A.	N.A.

Alg-Gel-HAp(1)	22G	1	4	N.A.	N.A.	N.A.	N.A.	N.A.
Alg-Gel-HAp(1)	22G	1	4	16	1220	0.946	0.852	3.592
Alg-Gel-HAp(1)	22G	2	2	16	1015	0.933	0.608	3.013
Alg-Gel-HAp(1)	22G	2	2	16	1147	0.928	0.792	3.430
Alg-Gel-HAp(1)	22G	2	2	16	1144	0.897	0.817	3.423
Alg-Gel-HAp(1)	22G	2	4	N.A.	N.A.	N.A.	N.A.	N.A.
Alg-Gel-HAp(1)	22G	2	4	N.A.	N.A.	N.A.	N.A.	N.A.
Alg-Gel-HAp(1)	22G	2	4	15	1102	0.923	0.654	3.107
Alg-Gel-HAp(1)	22G	3	2	16	1185	0.930	0.644	3.095
Alg-Gel-HAp(1)	22G	3	2	16	1078	0.932	0.707	3.246
Alg-Gel-HAp(1)	22G	3	2	16	1095	0.944	0.729	3.318
Alg-Gel-HAp(1)	22G	3	4	N.A.	N.A.	N.A.	N.A.	N.A.
Alg-Gel-HAp(1)	22G	3	4	N.A.	N.A.	N.A.	N.A.	N.A.
Alg-Gel-HAp(1)	22G	3	4	16	1267	0.941	0.929	3.740
Alg-Gel-HAp(2)	20G	1	2	14	988	0.874	0.608	2.914
Alg-Gel-HAp(2)	20G	1	2	14	1001	0.881	0.613	2.939
Alg-Gel-HAp(2)	20G	1	2	14	956	0.887	0.540	2.767
Alg-Gel-HAp(2)	20G	1	4	9	917	0.946	0.454	2.622
Alg-Gel-HAp(2)	20G	1	4	8	1030	0.980	0.558	2.959
Alg-Gel-HAp(2)	20G	1	4	8	907	0.931	0.443	2.569
Alg-Gel-HAp(2)	20G	2	2	16	1056	1.011	0.600	3.116
Alg-Gel-HAp(2)	20G	2	2	15	908	0.853	0.511	2.640
Alg-Gel-HAp(2)	20G	2	2	13	965	0.875	0.558	2.794
Alg-Gel-HAp(2)	20G	2	4	8	875	0.928	0.426	2.516
Alg-Gel-HAp(2)	20G	2	4	8	829	0.911	0.386	2.371
Alg-Gel-HAp(2)	20G	2	4	8	905	0.899	0.468	2.594
Alg-Gel-HAp(2)	20G	3	2	16	1005	0.886	0.586	2.882
Alg-Gel-HAp(2)	20G	3	2	13	907	0.868	0.486	2.597
Alg-Gel-HAp(2)	20G	3	2	15	943	0.876	0.518	2.695
Alg-Gel-HAp(2)	20G	3	4	8	879	0.902	0.437	2.511
Alg-Gel-HAp(2)	20G	3	4	8	927	0.891	0.492	2.649
Alg-Gel-HAp(2)	20G	3	4	8	951	0.930	0.485	2.686
Alg-Gel-HAp(2)	22G	1	2	16	1226	0.915	0.876	3.582
Alg-Gel-HAp(2)	22G	1	2	16	1142	0.910	0.767	3.341
Alg-Gel-HAp(2)	22G	1	2	16	1005	0.874	0.595	2.885
Alg-Gel-HAp(2)	22G	1	4	16	1017	0.885	0.616	2.955
Alg-Gel-HAp(2)	22G	1	4	15	978	0.882	0.551	2.788
Alg-Gel-HAp(2)	22G	1	4	16	1107	0.893	0.718	3.203
Alg-Gel-HAp(2)	22G	2	2	16	1202	0.906	0.862	3.534
Alg-Gel-HAp(2)	22G	2	2	16	1248	0.928	0.908	3.671
Alg-Gel-HAp(2)	22G	2	2	15	1102	0.923	0.654	3.107
Alg-Gel-HAp(2)	22G	2	4	14	999	0.975	0.510	2.821
Alg-Gel-HAp(2)	22G	2	4	13	1075	0.899	0.665	3.095
Alg-Gel-HAp(2)	22G	2	4	15	1158	0.885	0.794	3.353
Alg-Gel-HAp(2)	22G	3	2	16	1165	0.939	0.790	3.445

Alg-Gel-HAp(2)	22G	3	2	16	1316	0.931	0.978	3.817
Alg-Gel-HAp(2)	22G	3	2	13	1080	0.904	0.663	3.097
Alg-Gel-HAp(2)	22G	3	4	16	1163	0.883	0.823	3.409
Alg-Gel-HAp(2)	22G	3	4	16	1025	0.885	0.613	2.946
Alg-Gel-HAp(2)	22G	3	4	16	1226	0.915	0.876	3.582

N.A.: Not Applicable. Structural integrity and pore geometry could not be reliably quantified.


**Table S2.** ANOVA analysis for printability results

Response Variable	Factor	F	p-value	$\omega^2$	Sig.
Open Pores	HAp Level	55.17	<0.001	0.003	***
Open Pores	Nozzle	228.92	<0.001	0.011	***
Open Pores	Extrusion Speed	1.76	0.185	<0.001	ns
Open Pores	Num. Layers	204.63	<0.001	0.010	***
Pore Size ( $\mu\text{m}$ )	HAp Level	1.25	0.269	<0.001	ns
Pore Size ( $\mu\text{m}$ )	Nozzle	209.21	<0.001	0.009	***
Pore Size ( $\mu\text{m}$ )	Extrusion Speed	3.27	0.048	<0.001	*
Pore Size ( $\mu\text{m}$ )	Num. Layers	19.83	<0.001	0.001	***
Printability Index	HAp Level	21.40	<0.001	<0.001	***
Printability Index	Nozzle	3.78	0.058	<0.001	ns
Printability Index	Extrusion Speed	0.10	0.902	<0.001	ns
Printability Index	Num. Layers	0.49	0.489	<0.001	ns
Pore Area ( $\text{mm}^2$ )	HAp Level	2.50	0.122	<0.001	ns
Pore Area ( $\text{mm}^2$ )	Nozzle	202.50	<0.001	0.034	***
Pore Area ( $\text{mm}^2$ )	Extrusion Speed	3.01	0.060	0.001	ns
Pore Area ( $\text{mm}^2$ )	Num. Layers	27.80	<0.001	0.005	***
Pore Perimeter (mm)	HAp Level	7.84	0.008	<0.001	**
Pore Perimeter (mm)	Nozzle	176.05	<0.001	0.008	***
Pore Perimeter (mm)	Extrusion Speed	2.62	0.084	<0.001	ns
Pore Perimeter (mm)	Num. Layers	26.65	<0.001	0.001	***

Effect sizes reported as omega-squared ( $\omega^2$ )

\*\*\*p < 0.001, \*\*p < 0.01, \*p < 0.05, ns = not significant

n = 66 observations

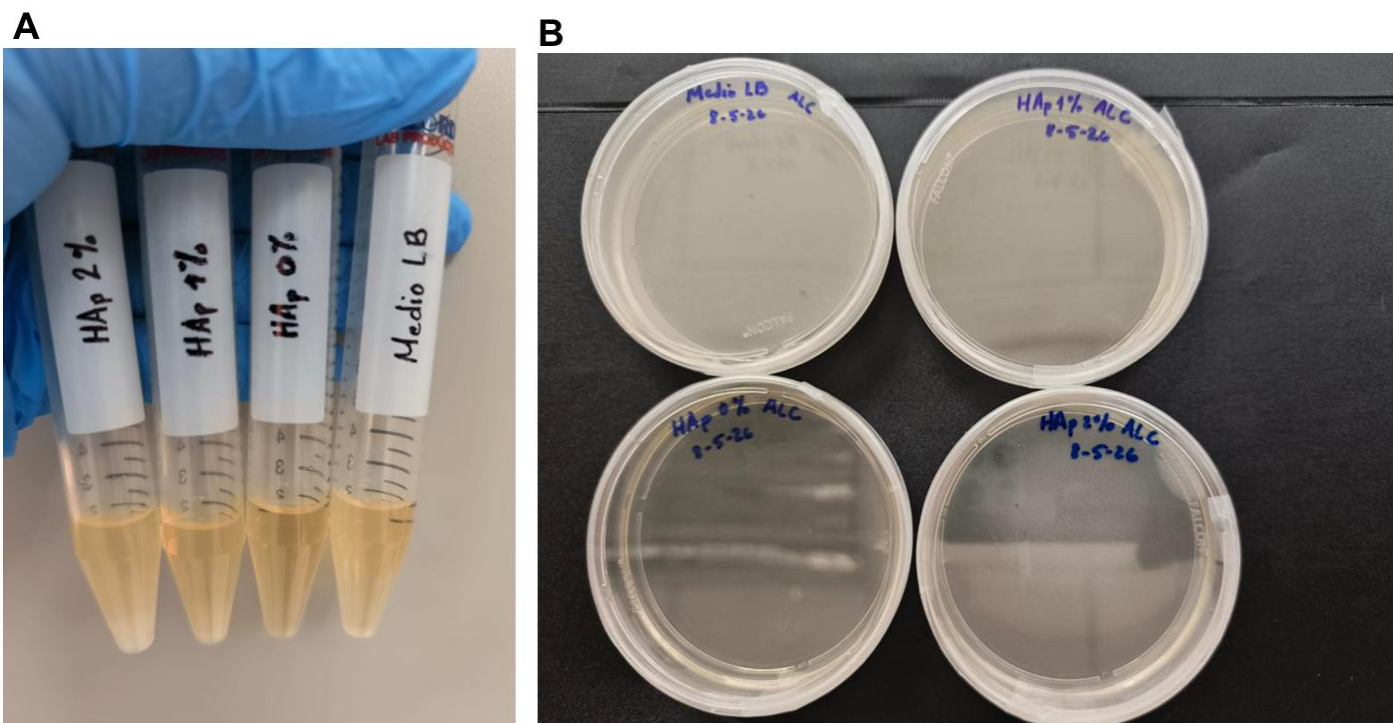

**Figure S1.** Microbiological sterility assessment of composite biomaterial formulations after UV irradiation. (A) Visual appearance of liquid Lysogeny Broth (LB) medium inoculated with 0% (control), 1%, and 2% HAp formulations after 72h of incubation at 37 °C demonstrating media translucency and absence of macroscopic turbidity. (B) Representative macrographs of solid LB-agar plates showing zero colony-forming units (CFU) after 72 h, confirming the absolute efficacy of the sterilization protocol and aseptic handling prior to cell encapsulation.